

AD-A209 529

REPORT DOCUMENTATION PAGE

2

3712 FILE (11P)

2b. DECLASSIFICATION/DOWNGRADING SCHEDULE

1b. RESTRICTIVE MARKINGS
None

3. DISTRIBUTION/AVAILABILITY OF REPORT
Unlimited

4. PERFORMING ORGANIZATION REPORT NUMBER(S)

interim 27

5. MONITORING ORGANIZATION REPORT NUMBER(S)

6a. NAME OF PERFORMING ORGANIZATION
Department of Chemistry

6b. OFFICE SYMBOL
(if applicable)

7a. NAME OF MONITORING ORGANIZATION
Office of Naval Research

6c. ADDRESS (City, State, and ZIP Code)
Massachusetts Institute of Technology
77 Mass. Avenue, Bldg. 6-335
Cambridge, MA 02139

7b. ADDRESS (City, State, and ZIP Code)
Chemistry Division
800 N. Quincy Street
Arlington, VA 22217

8a. NAME OF FUNDING/SPONSORING
ORGANIZATION
Office of Naval Research

8b. OFFICE SYMBOL
(if applicable)

9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER
N00014-84-K-0553

8c. ADDRESS (City, State, and ZIP Code)
Chemistry division
800 N. Quincy Street
Arlington, VA 22217

10. SOURCE OF FUNDING NUMBERS

PROGRAM ELEMENT NO.	PROJECT NO.	TASK NO.	WORK UNIT ACCESSION NO.
		051-579	

11. TITLE (Include Security Classification)

Microfabrication of WO₃-Based Microelectrochemical Devices

12. PERSONAL AUTHOR(S) Martin O. Schloh, Nicholas Leventis and Mark S. Wrighton

13a. TYPE OF REPORT
technical interim

13b. TIME COVERED
FROM 6/1/88 TO 6/12/89

14. DATE OF REPORT (Year, Month, Day)
June 12, 1989

15. PAGE COUNT
21

16. SUPPLEMENTARY NOTATION

Prepared for publication in Applied Physics Letters.

17. COSATI CODES

FIELD	GROUP	SUB-GROUP

18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)

Photolithography, tungsten oxide, modified microelectrode arrays

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

See Attached Sheet

DTIC
ELECTE
JUN 27 1989
S E D

20. DISTRIBUTION/AVAILABILITY OF ABSTRACT

☐ UNCLASSIFIED/UNLIMITED ☐ SAME AS RPT. ☐ DTIC USERS

21. ABSTRACT SECURITY CLASSIFICATION
Unlimited

22a. NAME OF RESPONSIBLE INDIVIDUAL
Mark S. Wrighton

22b. TELEPHONE (Include Area Code)
617-253-1597

22c. OFFICE SYMBOL

89

6 27 013

Office of Naval Research

Contract N00014-84-K-0553

Task No. 051-597
Technical Report #29

Microfabrication of WO_3 -Based Microelectrochemical Devices

by

Martin O. Schloh, Nicholas Leventis, and Mark S. Wrighton

Prepared for Publication

in

Applied Physics Letters

Massachusetts Institute of Technology
Department of Chemistry
Cambridge, MA 02139

June 12, 1989

Reproduction in whole or in part is permitted for
any purpose of the United States Government

This document has been approved for public release
and sale; its distribution is unlimited

[Prepared for Publication as a Letter in Applied Physics
Letters]

Microfabrication of WO₃-Based Microelectrochemical Devices

Martin O. Schloh, Nicholas Leventis, and Mark S. Wrighton*

*Department of Chemistry
Massachusetts Institute of Technology
Cambridge, Massachusetts 02139*

* Address all correspondence to this author.

Abstract


A new photolithographic process for the patterning of WO_3 is reported. A layer of RF sputtered polycrystalline WO_3 can be patterned by a combination of photolithographic and dry etching processes to selectively cover a fraction of eight Pt microelectrodes each $\sim 50 \mu\text{m}$ long, $2 \mu\text{m}$ wide, and $0.3 \mu\text{m}$ thick and spaced $1.2 \mu\text{m}$ apart. The modified microelectrode arrays were characterized by electrochemistry, by surface profilometry, and by scanning electron microscopy. A pair of microelectrodes connected by WO_3 comprises a microelectrochemical transistor with pH-dependent electrical characteristics based on the pH and potential dependent conductivity of WO_3 associated with the reversible electrochemical reaction

$$\text{WO}_3 + n\text{H}^+ + ne^- \rightleftharpoons \text{H}_n\text{WO}_3.$$

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Dist	Avail and/or Special
A-1	




We wish to report a new microfabrication process for the selective modification of microelectrode arrays with a polycrystalline WO_3 film. Microelectrode arrays consisting of eight closely-spaced ($\sim 1.2 \mu\text{m}$ apart) Pt microelectrodes ($\sim 50 \mu\text{m}$ long, $2 \mu\text{m}$ wide, and $0.3 \mu\text{m}$ thick) have been fabricated and used in our laboratory for the study of redox active polymers^{1,2} and inorganic materials.²⁻⁵ A pair of microelectrodes connected by a redox active material can be used as a chemically sensitive transistor, because the conductivity of the redox active material depends on its state of charge.⁶ For example, the WO_3 -based device illustrated in Scheme I³ is a pH-sensitive transistor by virtue of a pH dependence of the potential at which reduction occurs³ to give conducting H_nWO_3 ,⁷⁻¹⁰ equation (1). The WO_3 -based transistor shows variations in I_D - V_G



characteristics depending on pH and, therefore, can be used to detect pH changes at fixed V_G .³


Microfabrication technology^{11,12} is a possible route to preparation of large numbers of WO_3 -based devices showing the same electrical characteristics. In this article we report a process for high resolution ($\sim 1 \mu\text{m}$) patterning of WO_3 that yields selective modification of a microelectrode array. The results show that reproducible microelectrochemical response can be obtained and that

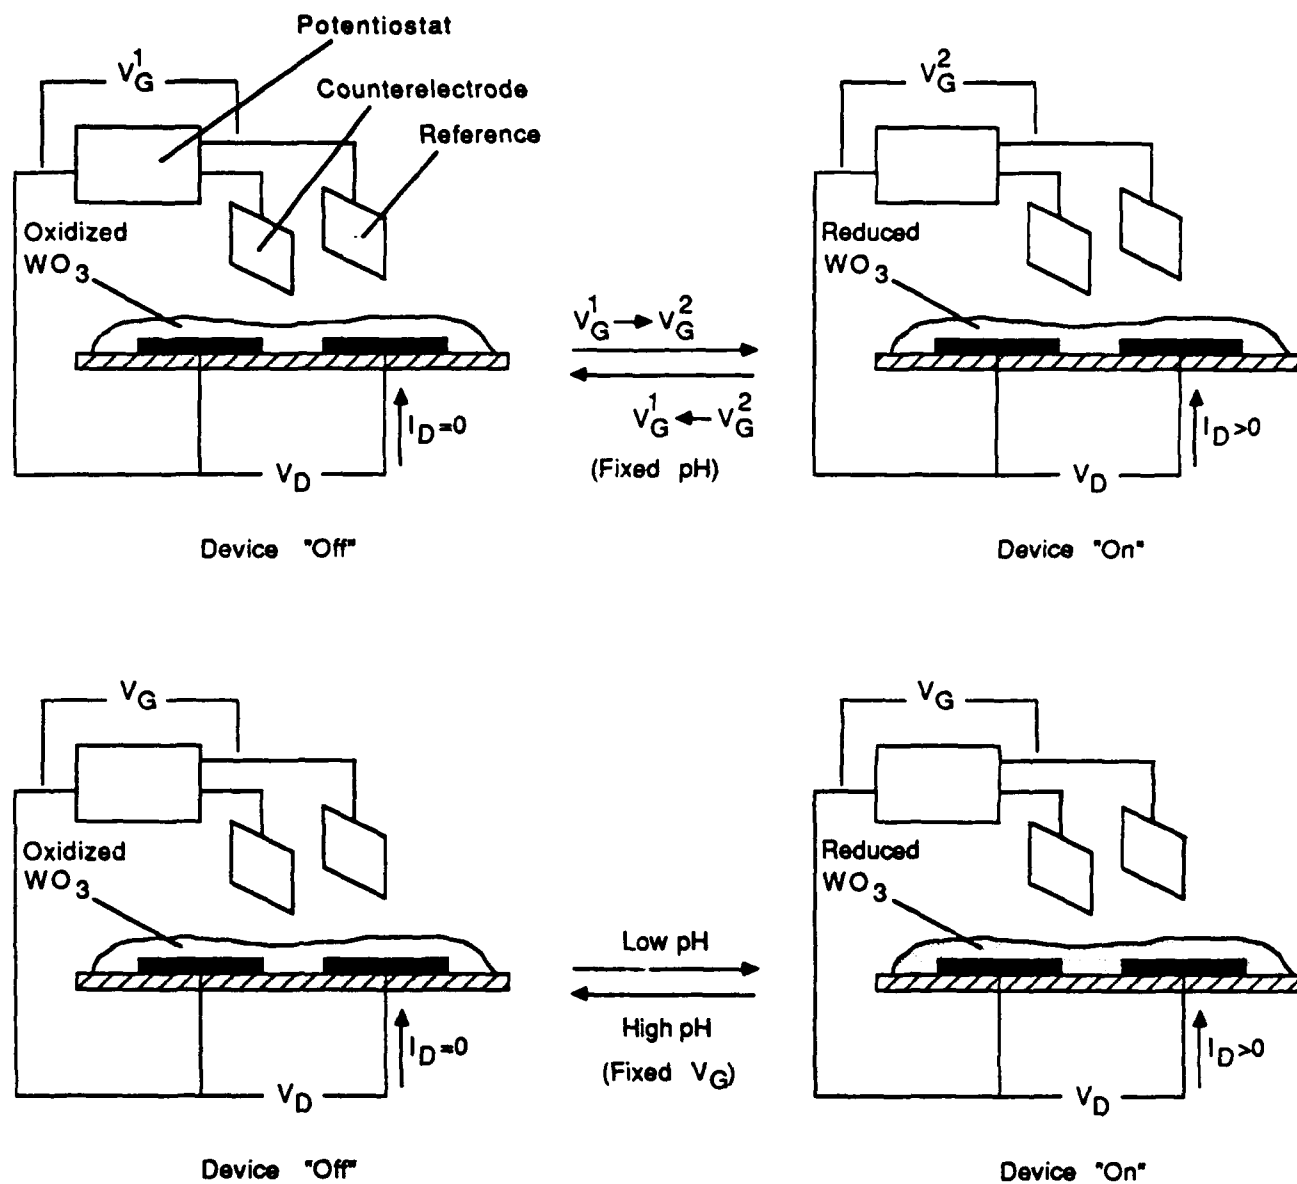

Scheme I. A WO_3 -based transistor that turns on ($I_D > 0$) when V_G is moved from V_G^1 where WO_3 is oxidized and insulating to V_G^2 where WO_3 is reduced and conducting. The WO_3 -based device can also be turned on and off by varying the pH at fixed V_G .

non-modified microelectrodes can be left available for further functionalization. In addition to applications for microelectrochemical sensors the process may be applicable to high resolution electrochromic devices based on WO_3 .⁷ The patent literature contains various techniques for patterning WO_3 including deposition through masks¹³ and etching by dissolution of WO_3 in alkaline solutions.¹⁴ Such techniques, though, seem to be limited to linewidths of several millimeters. Other techniques involve polymer coordinated tungsten compounds ashed to the oxide by pyrolysis. This procedure is claimed to achieve $\sim 5 \mu\text{m}$ resolution, but the quality of the WO_3 is not mentioned.¹⁵ Our method of WO_3 patterning involves using photoresist to protect WO_3 and etching of unwanted WO_3 . The etching process via an SF_6 plasma was deemed attractive, because likely W/O/F compounds, namely WF_6 and WOF_4 , which might be formed by reaction of WO_3 with F· atoms generated in the SF_6 plasma, are volatile.¹⁶ Importantly, the SF_6 plasma does not as rapidly etch organics^{11,12} so that areas of WO_3 protected by photoresist will survive the etching process.

Scheme II summarizes the process that has been developed for selective modification of a Pt microelectrode array with WO_3 . The process for preparation of the Pt microelectrode array has been reported previously,¹⁻⁶ and such arrays consist of eight, individually addressable Pt microelectrodes each $\sim 50 \mu\text{m}$ long x $\sim 2 \mu\text{m}$ wide x $\sim 0.3 \mu\text{m}$ thick and separated from each other by $\sim 1.2 \mu\text{m}$. Before

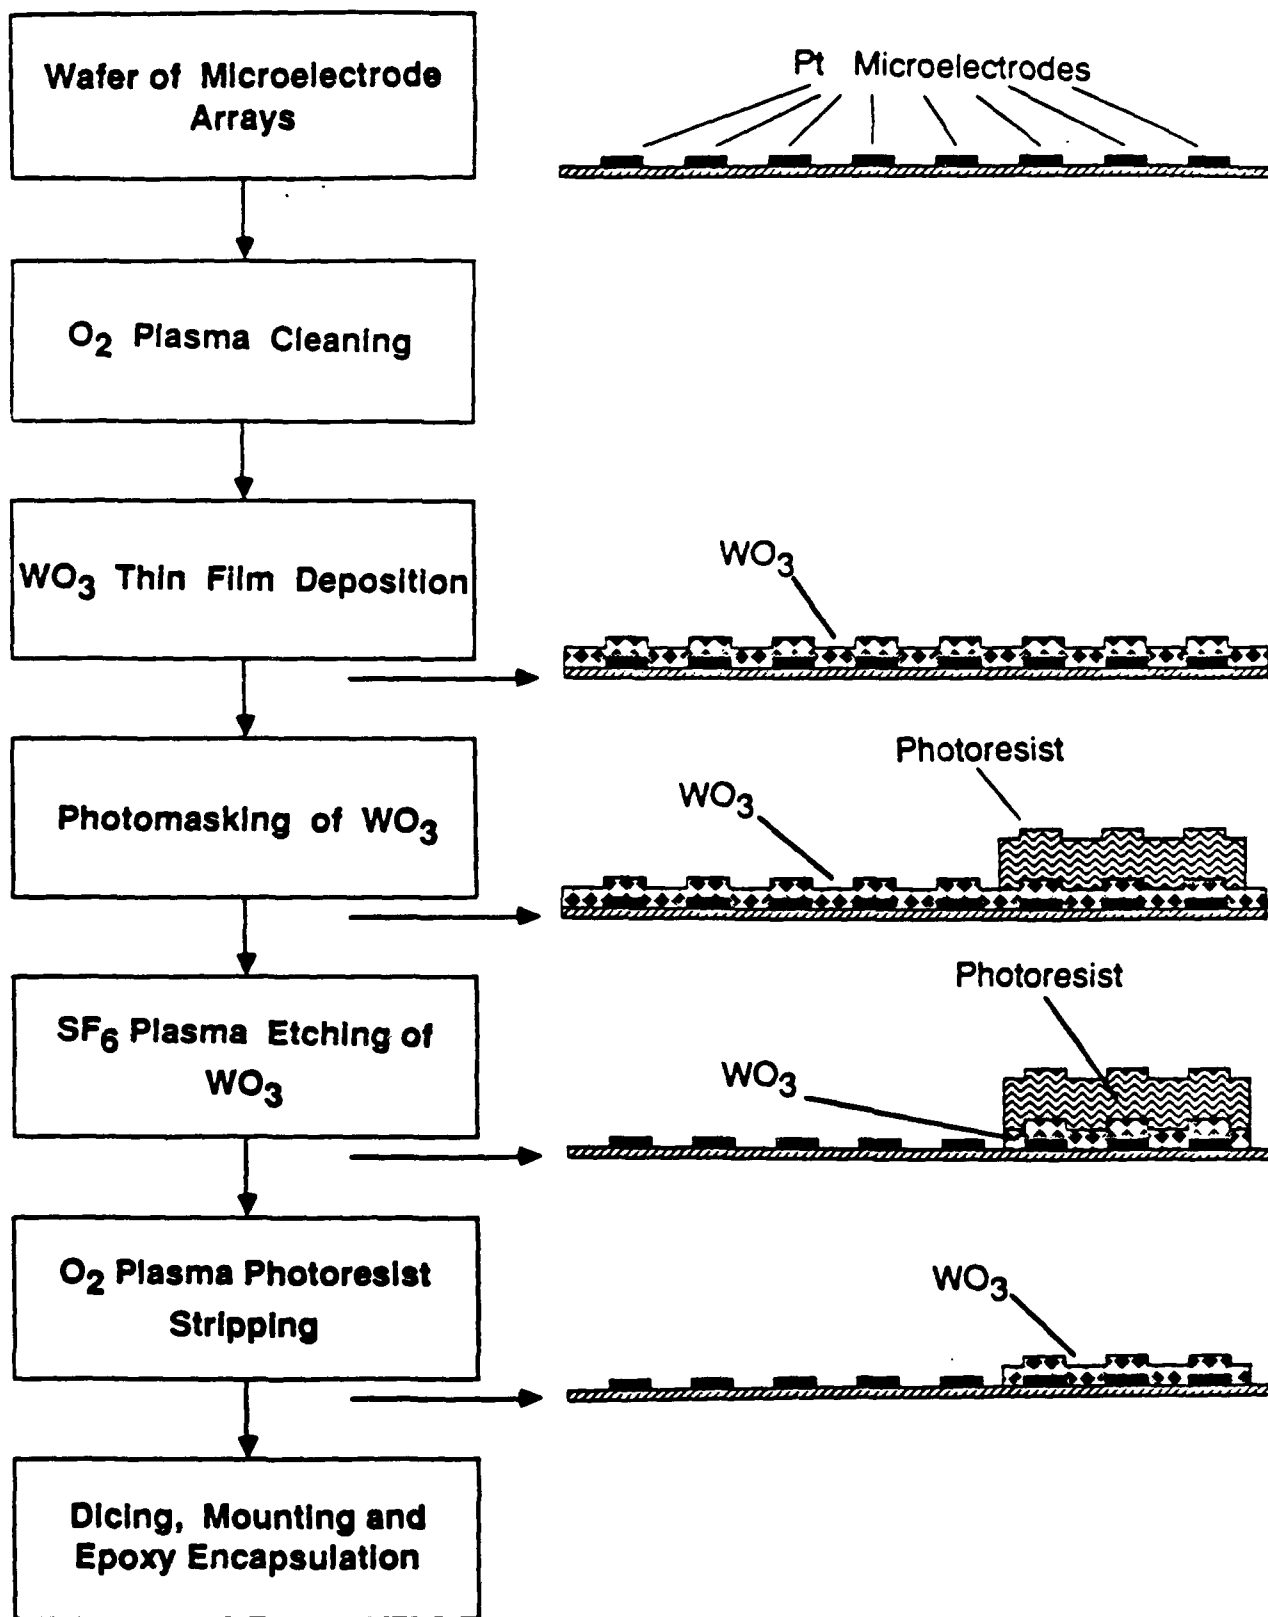

Scheme II. Process for selective modification of a Microelectrode Array with WO₃.

WO₃-deposition Si wafers carrying Pt microelectrode arrays were cleaned in an O₂ plasma using a Harrick Plasma Cleaner. Using a process previously described,³ the entire wafer was coated with a ~0.3 μm conformal coating of WO₃.

The WO₃-coated samples were dried at 200 °C for 30 min (dehydration bake). Positive photoresist KTI 1370SF was syringed onto the wafers which were then spun at 3000 rpm for 30 seconds. After a 25 min soft bake at 90 °C the wafers were exposed through a mask with ~8 mW/cm² intensity at 320 nm for 45 seconds using a Karl Suss High Resolution Aligner. The mask used was designed to allow exposure of all photoresist except that covering the desired pattern of WO₃, Scheme II. The photoresist was developed for 60 seconds in a 1:1 mixture of KTI 312 positive photoresist developer and deionized H₂O, followed by extensive rinse with deionized H₂O and air-blow drying. The photoresist protecting desired WO₃ was hard-baked at 135 °C for 25 min. The unprotected WO₃ was completely etched away in an SF₆ plasma at 200 W forward power for approximately 4 min. Finally the protective photoresist layer on top of WO₃ was removed in an O₂ plasma at 300 W forward power for 6 min. The O₂ plasma does not attack WO₃.

Figure 1 shows the photomask layout for patterning WO₃ in the fabrication of one microelectrode array. Surface profiling indicates that a ~0.3 μm thick layer of material conformally coats three electrodes of the microelectrode array, and SEM pictures demonstrate that material,

presumably WO_3 , has been deposited where we originally intended to confine it. Proof for the composition of this material is deduced from the Auger electron spectroscopy and the electrochemical response of the WO_3 in aqueous solution. Additionally, Auger shows that WO_3 is completely removed by the SF_6 plasma from areas not protected by photoresist.

Microfabricated WO_3 -based devices have been characterized by cyclic voltammetry in various buffered aqueous solutions, Figure 2. The position and the shape of the reduction wave of WO_3 , as expected from equation (1), depend on the availability of the intercalating species,³ i.e. H^+ . The onset of reduction shifts to more negative potentials as the proton concentration decreases.

The fact that all the microelectrodes that appear connected with WO_3 in the SEM picture give identical response, when driven individually or when driven together, confirms that these microelectrodes are connected with WO_3 in the electrical sense.¹⁻⁶ Microelectrodes 1 through 5, which are supposed to be clean of WO_3 show no electrochemical response characteristic of WO_3 , consistent with the absence of WO_3 from Auger electron spectroscopy. The cyclic voltammetry results are the same as previously reported from non-patterned WO_3 deposited in the manner used here.³

Taking the voltage between WO_3 and the reference electrode (SCE) as the gate voltage, V_G , the WO_3 itself can, in analogy to a Si MOSFET, be thought of as the channel.⁶

Applying a small drain voltage, $V_D = 25$ mV, between two adjacent microelectrodes connected with WO_3 , Scheme I, we observe, Figure 3, an increasing drain current, I_D , as WO_3 is progressively driven to a more negative potential. Figure 3 also shows the effect of $[H^+]$ on the threshold voltage of I_D in various aqueous solutions. The WO_3 -based devices described here are pH sensitive in the sense that a change in the pH alters the drain current at a given V_G , as previously reported.³ Finally, the electrochemical and electronic response of the WO_3 -based devices confirm that the photolithographically processed WO_3 retains the essential properties of the material.

In summary, we have demonstrated a photolithographic/dry etching process for patterning WO_3 in a dimensional regime routinely employed in VLSI technology. Using this process we are able to confine WO_3 over a defined fraction of electrodes of a microelectrode array to produce a pH-sensitive microelectrochemical transistor. Significantly, the new process allows the rapid preparation of a large number of microelectrochemical devices having the same electrical characteristics. Moreover, the process leaves a fraction of microelectrodes of the array available to achieve a low level of integration of microelectrochemical devices by further functionalization of the array.

We thank the Office of Naval Research and the Defense Advanced Research Projects Agency for support of this

research. Use of the RF sputtering facility at E.I.C. Labs, Dedham, Massachusetts is gratefully acknowledged. We also thank James J. Hickman for valuable Auger electron spectroscopy measurements.

References

- ¹H. S. White, G. P. Kittlesen, and M. S. Wrighton, J. Am. Chem. Soc. **106**, 5375 (1984).
- ²E. W. Paul, A. J. Ricco, and M. S. Wrighton, J. Phys. Chem. **89**, 1441 (1985).
- ³M. J. Natan, T. E. Mallouk, and M. S. Wrighton, J. Phys. Chem. **91**, 648 (1987).
- ⁴M. J. Natan, D. Bélanger, M. K. Carpenter, and M. S. Wrighton, J. Phys. Chem. **91**, 1834 (1987).
- ⁵D. F. Lyons, M. O. Schloh, J. J. Hickman, and M. S. Wrighton, J. Phys. Chem., submitted.
- ⁶M. S. Wrighton, Comments on Inorg. Chem. **4**, 269 (1985).
- ⁷W. C. Dautremont-Smith, Displays **3**, 3 (1982).
- ⁸B. Reichman, A. J. Bard, and D. J. Laser, J. Electrochem. Soc. **127**, 647 (1980).
- ⁹W. C. Dautremont-Smith, M. Green, and K. S. Kong, Electrochim. Acta **22**, 751 (1977).
- ¹⁰R. S. Crandall, B. W. Faughnan, Phys. Rev. Lett. **39**, 232 (1977).
- ¹¹S. M. Sze, ed., *VLSI Technology*, McGraw-Hill, 1983, p.324.
- ¹²S. K. Ghandi, *VLSI Fabrication Principles*, John Wiley & Sons, 1983.
- ¹³P. M. Heyman, R. L. Quin, and I. Goroy, U.S. Patent No. 3 981 560 (1976).

¹⁴K. Y. Tenri, Y. I. Nishinomiya, H. H. Tenri, and H. U. Wakayama, U.S. Patent No. 4 123 841 (1978).

¹⁵Chem. Abstracts **101**, 181267q (1984).

¹⁶F. A. Cotton, and G. Wilkinson, Advanced Inorganic Chemistry, 4th Edition, John Wiley & Sons, p. 861 and p. 866.



Figure Captions

Figure 1. Comparison of the photomask used for the WO_3 confinement and the actual devices, as characterized by surface profilometry and SEM. (A) Photomask layout for the patterning of WO_3 over three electrodes of an eight microelectrode array; (B) Surface profile; the stylus begins on the Si_3N_4 encapsulation layer (1), moves to the Pt protective barrier (2), and to the individual microelectrodes (3) three of which are coated conformally with $\sim 0.3 \mu\text{m}$ of WO_3 ; (C) SEM of one chip produced by the process shown in Scheme II.


Figure 2. Cyclic voltammograms of patterned WO_3 on electrodes #6, 7, and 8 (cf. Figure 1) in aqueous 1.0 M HClO_4 as a function of sweep rate. The fact that #6, 7, or 8 give the same response and the same response as #6-8 driven together shows that all of the WO_3 is accessible by addressing any one of the three WO_3 -coated and connected electrodes. Microelectrodes #1-5 show no detectable WO_3 at 500 mV/s.

Figure 3. I_D - V_G characteristics of a WO_3 -based transistor (cf. Figure 1 and Scheme I) in several aqueous electrolytes showing that the threshold value of V_G shifts with pH;


pH \approx 0 (0.5 M H_2SO_4 and 1.0 M HClO_4) and pH \approx 7 (phosphate buffer and 0.1 M NaClO_4).

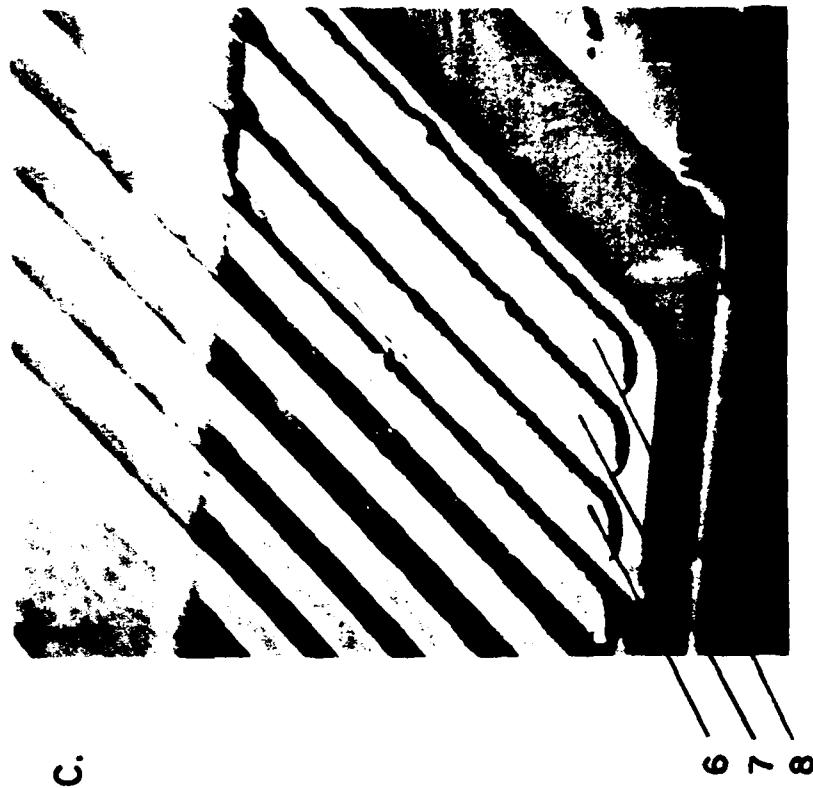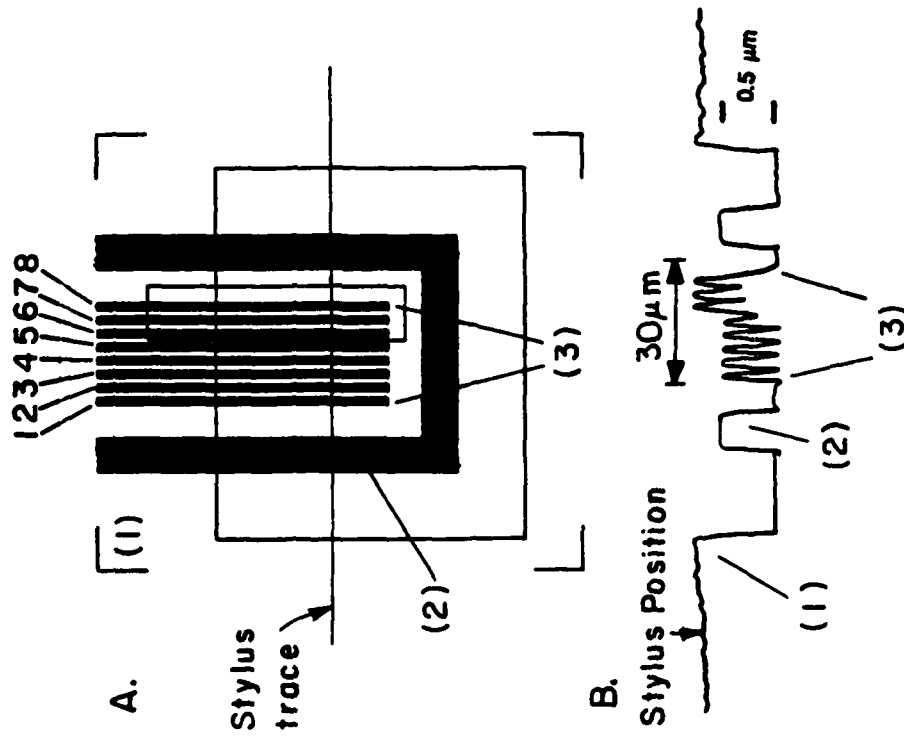


Cyclic Voltammetry of a Three Electrode Confined, WO_3 - Based Device in H_2O , 1.0 M HClO_4

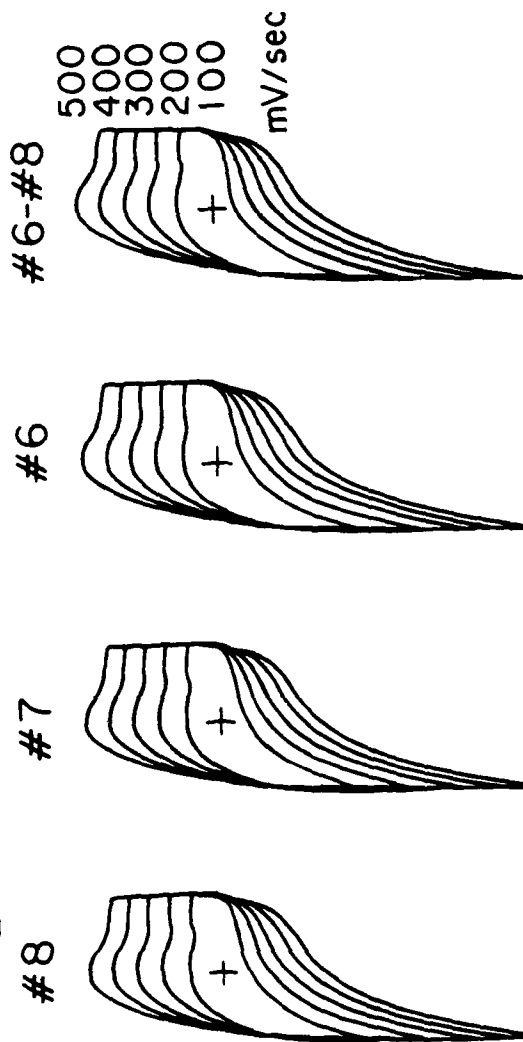

#1-#5 at 500mV/sec

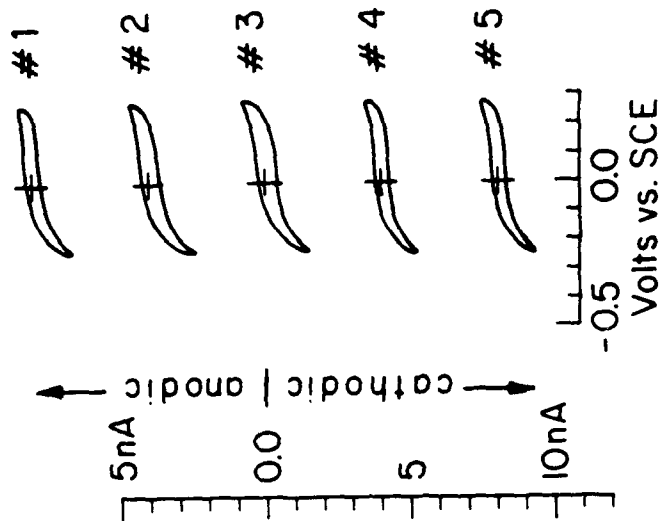

-0.5 0.0
Volts vs. SCE

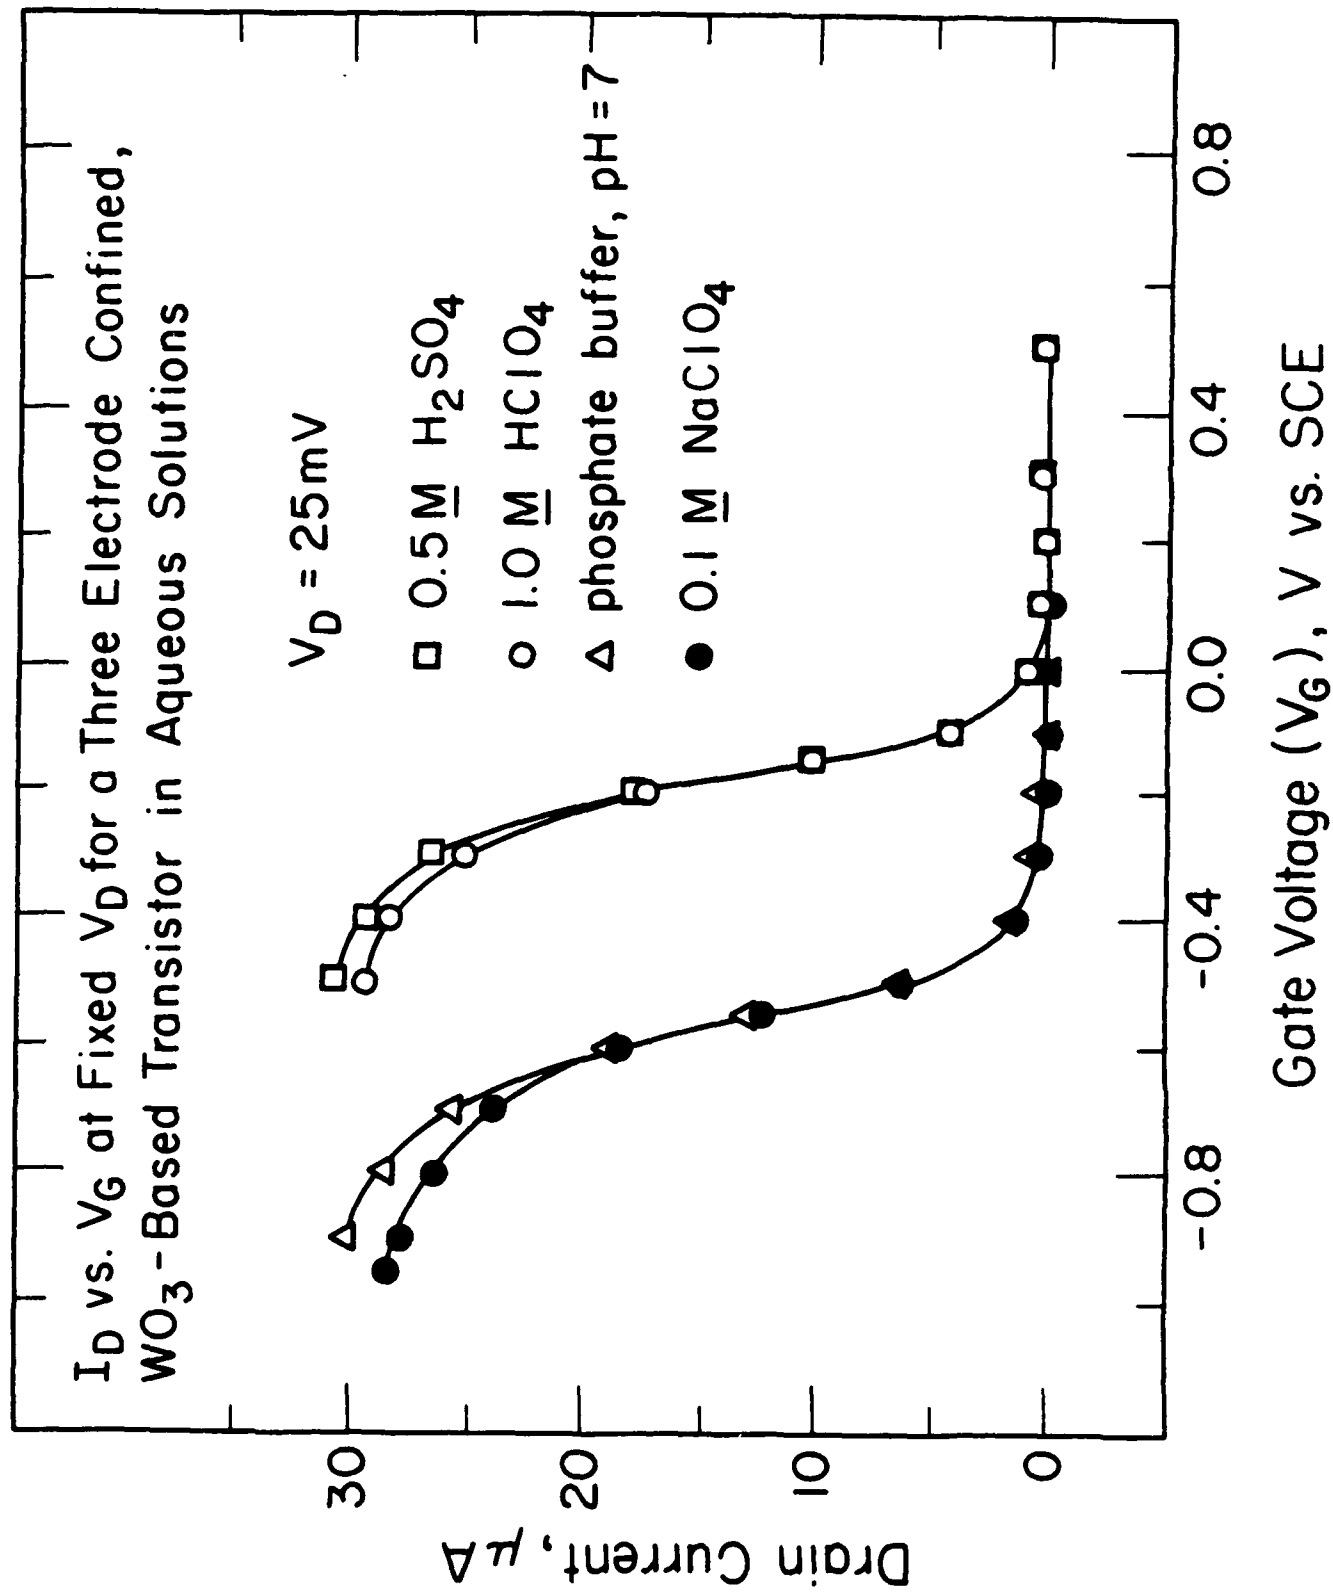

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1